



The Forging of Dispersed Nano-Emulsion for Potential Feed Additive from Black Soldier Fly Essential Oil by Ultrasonication and Its Biological Efficacy

Novia Amalia Sholeha, Tekad Urip Pambudi Sujarnoko, Lilis Khotijah, Dewi Apri Astuti*, Muhamad Baihaqi, and Kokom Komalasari

Received : May 6, 2025

Revised : September 4, 2025

Accepted : December 4, 2025

Online : February 16, 2026

Abstract

Encapsulation technology was developed to address the issues of limited bioavailability and instability associated with black soldier fly oil (BSFO). This research synthesized a nano-emulsion of BSFO utilizing the ultrasonication method, while varying the sources of antioxidants (black seed oil (BSO) and curcumin) and emulsifiers (polyethylene glycol (PEG), whey protein isolate, and Tween 80). The FTIR analysis revealed that the nanoemulsion samples displayed peaks at 3500–3000 cm^{-1} (O–H stretching), 2900–2700 cm^{-1} (N–H stretching), and 1700–1500 cm^{-1} (C=O stretching), suggesting the presence of BSFO, curcumin, BSO, and the characteristics of the emulsifiers. Particle size analysis (PSA) indicated that the emulsion had an average particle size (Z-average) of approximately 229–686 nm. The nanoemulsion containing PEG showed reduced particle sizes of 218 and 229 nm compared to those with other emulsifiers, attributable to the inherently smaller size of PEG. The HB (BSO with PEG emulsifier) showed a reduced particle size due to the smaller molecular size of the antioxidant BSO compared to curcumin. The polydispersity index (PI) values for HB and CB (curcumin with PEG emulsifier) were 0.3 and 0.2, respectively, indicating relatively homogeneous particles, consistent with the criterion of a PI value below 0.4. Biological assays showed that CB had the highest DPPH inhibition at 83%, while curcumin exhibited 90%, exceeding that of BSO. The inhibition zones of HB are 2.45 cm for *Staphylococcus aureus* and 2.70 cm for *Escherichia coli*, representing the highest levels of inhibition. In this study, PEG is the best emulsifier for achieving a smaller nanoemulsion particle size. PEG facilitates the incorporation of BSFO with antioxidants, enhancing stability, efficacy, and bioavailability in various applications, particularly in the medical and food sectors.

Keywords: black seed oil, black soldier fly oil, curcumin, nano-emulsion, ultrasonic-assisted extraction

1. INTRODUCTION

The increasing global population raises concerns regarding the food supply chain and its implications for climate change. The anticipated global demand for agricultural products is projected to rise by 15% within the next decade, leading to an expected increase in the environmental footprint of the food system by 60–90% from 2010 to 2050 [1]. Locating alternative protein sources, particularly from insects, is crucial for manufacturing sustainable goods globally in the current context. Due to their high protein content and efficient feed conversion rates, insects are increasingly recognized as sustainable and nutritionally valuable sources of

animal feed [2][3]. Insect proteins may substantially replace conventional soybean and fish meal in animal feed [4]. The beneficial characteristics of one of order *Diptera*, *Hermetia illucens* Linnaeus, black soldier fly (BSF), are particularly notable, particularly the larvae's high protein and fat content [5]. Moreover, the application of BSF larvae in animal feed is enhanced by the substantial amounts of bioactive substances they contain, such as antimicrobial peptides and cellulose [6]. For oil chemicals, encapsulation techniques are useful tactics that are necessary to preserve their effectiveness during preparation and preservation [7][8]. While enabling tailored distribution to particular areas, including the digestive system, these methods are essential for reducing the negative impacts of pH level changes, heat-induced stress, water level, and the oxidation process [5][8]-[10]. BSF oils (BSFO) can also be supplemented with antioxidant compounds such as curcumin or black seed oil (BSO) [11][12]. On the other hand, curcumin (1,7-bis(4-hydroxy-3-methoxyphenyl) 1,6-heptadiene-3,5-dione) is a polyphenolic compound of low molecular weight, derived from the rhizome of *Curcuma longa* L., and is well known for its antibacterial, anti-inflammatory, and antioxidant

Publisher's Note:

Pandawa Institute stays neutral with regard to jurisdictional claims in published maps and institutional affiliations.



Copyright:

© 2026 by the author(s).

Licensee Pandawa Institute, Metro, Indonesia. This article is an open access article distributed under the terms and conditions of the Creative Commons Attribution (CC BY) license (<https://creativecommons.org/licenses/by/4.0/>).

Table 1. Samples composition.

Samples Code	Emulsifier Type	BSFO (v/v)	BSO (v/v)	Curcumin (w/v)	NaCl Solution (%)
HT	Tween 80 (10% v/v)	7.5	7.5	-	75
HW	WPI 2% (w/v)	7.5	7.5	-	85
HB	PEG 2% (w/v)	7.5	7.5	-	85
CT	Tween 80 (10% v/v)	15	-	0.1	75
CW	WPI 2% (w/v)	15	-	0.1	85
CB	PEG 2% (w/v)	15	-	0.1	85

properties [13]-[16]. The medicinal plant *Nigella sativa*, often known as black seed oil, belongs to the family of Ranunculaceae and is mostly grown in the Middle East and Southwest Asia for its anti-diabetic, anti-allergic, antioxidant, and anti-carcinogenic qualities [11][12].

There are several different encapsulation techniques, including micro- and nano-encapsulation, which are classified according to the size of the materials being encapsulated [17][18]. Encapsulation technologies play a critical role in overcoming the limitations of active compound delivery [19]. Protein-based micro- and nano-encapsulation, particularly those utilizing elastin-derived materials, offer notable advantages including enhanced chemical adaptability, biodegradability, and targeted delivery efficiency [20]-[22]. Colloidal systems known as nanoemulsions are made up of ultrafine particles that are typically smaller than 500 nm in diameter. Oil-in-water (O/W) nanoemulsions are created by dispersing tiny oil droplets in an aqueous phase that is continuous. The encapsulation of physiologically active substances is made possible by a surfactant, which separates the lipid core from the aqueous phase and integrates them into the oil [23][24]. The durability of the resulting nanostructure, the size of the particles, and the effectiveness of the created protective barrier are all significantly impacted by the emulsifier selection [25]. Additionally, it can increase the antioxidant capacity of compounds that are encapsulated, protect them from deterioration, and increase their bioavailability. Nanoemulsions are widely applied in cosmetics, pharmaceuticals (particularly in drug delivery), and the food industries [26]. The implementation of nanostructure acquisition techniques in food

technology enables the development of foods with novel chemical, biological, and physical attributes [27][28]. This innovation has positive social and economic effects in addition to expanding the selection of "smart" and "functional" meals. Nevertheless, this technology is complex, and its industrial application requires a multidisciplinary approach and consideration of numerous factors that influence product properties.

A nanoemulsion system is composed of multiple components, including surfactants, oil phase, and water phase [29]-[32]. A crucial factor to consider is the selection of the suitable emulsifier, such as tween 80 [33][34], whey protein [35]-[38], and polyethylene glycol (PEG) [39]. Tween 80, a non-ionic surfactant, is extensively utilized for its significant hydrophilicity and capacity to decrease interfacial tension, thereby facilitating the formation of stable small droplets [33]. Whey protein functions as a natural biopolymer emulsifier, forming a viscoelastic interfacial film that enhances physical stability and provides a more biocompatible alternative [37]. It was reported that PEG contributes to steric stabilization via its polymeric structure, which aids in preventing droplet aggregation and improving the long-term stability of nanoemulsions [39].

Sonication is a commonly utilized method that uses high-frequency sound waves and significant vibrational energy to disrupt and disperse particles, thereby facilitating the formation of nanoemulsions [29][40]. Extending sonication duration and adjusting the wave amplitude effectively reduce particle size in the nanoemulsion system, leading to more uniform droplet distribution and enhanced stability [4][37]. Treatment of a mixture within its ideal time range can improve the homogeneity of

particle size. The sonication method was selected due to its superior efficiency in generating nano-sized particles when compared to traditional techniques. This study investigates novel encapsulation techniques for BSFO-based nanoemulsions created with different emulsifiers, highlighting the role of bacterial activity in their development.

Sonication is a commonly utilized method that uses high-frequency sound waves and significant vibrational energy to disrupt and disperse particles, thus aiding in the formation of nanoemulsions [29] [40]. Increasing the duration of sonication and modifying wave amplitude significantly decreases particle size in the nanoemulsion system, resulting in a more uniform droplet distribution and improved stability [4][37]. Particle-size homogeneity is further improved when a mixture is treated within its ideal time range. In contrast to other nanoemulsification methods like high-pressure homogenization, which necessitates expensive equipment and may result in thermal degradation, and micro fluidization, which frequently requires multiple passes and high operational energy, the sonication method was chosen because of their effectivity at producing nano-sized droplets. Sonication, on the other hand, provides precise control over droplet production and is a more accessible and energy-efficient method. In this work, new encapsulating techniques

for BSFO-based nanoemulsions made using various emulsifiers are examined. The biological activity of BSFO, especially its antibacterial actions against *Escherichia coli* and *Staphylococcus aureus*, along with its antioxidant capabilities, constitutes the principal justification for encapsulation. Nano emulsification can augment the bioavailability of these bioactive constituents, safeguard them against degradation, and raise their functional efficacy during application. Therefore, an understanding of how emulsifier type and sonication settings affect the stability and preservation of antioxidant and antibacterial properties in BSFO is necessary to support the overall purpose of this work.

2. MATERIALS AND METHODS

2.1. Materials

The materials used in this study included physiological saline solution (0.9% w/v NaCl; PT Emjebe Pharma); BSFO (7.5–15% v/v); curcumin (0.1% w/v); BSO (7.5% w/v); Tween 80 (polyoxyethylene sorbitan monooleate, polysorbate 80; Merck); whey protein isolate (WPI); PEG (polyethylene glycol hexadecyl ether; Merck); 2,2-diphenyl-1-picrylhydrazyl (DPPH, analytical grade, Sigma-Aldrich), toluene (analytical grade, Merck); Gram-positive *S. aureus* ATCC 25923 and Gram-negative *E. coli* ATCC 25922 along with nutrient agar (NA, HiMedia) as the culture medium for

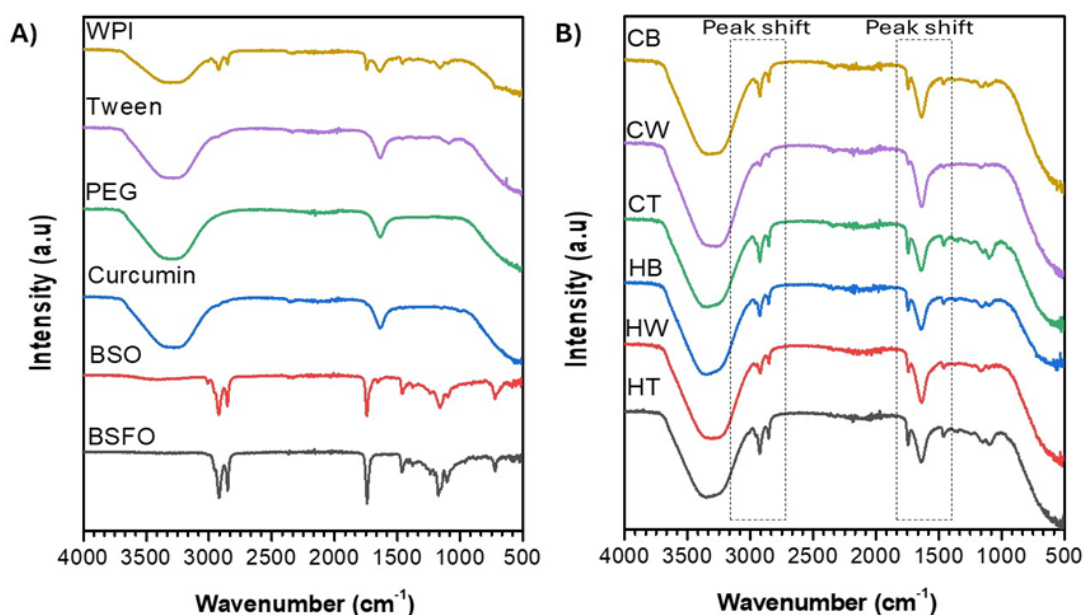


Figure 1. FTIR analysis of (A) precursor and (B) nanoemulsion with different emulsifiers.

antibacterial analysis.

2.2. Methods

2.2.1. Formulation of Nanoemulsion

The emulsifier constituted 2% of the total formulation by weight and was solubilized in an 85% physiological NaCl solution through stirring under 60 °C for 30 min. The solution was supplemented with 7.5% BSFO and 7.5% BSO, and then sonicated using an ultrasonic homogenizer (Sonicator, Labtron Equipment Ltd, UK), with the probe positioned between the two phases to expedite the creation of nanoemulsions based on the formulation in Table 1. The process was carried out for 30 min.

2.2.2. Characterization of Nanoemulsion

A Fourier-transform infrared (FTIR-8400S, Shimadzu, Japan) spectrophotometer was used to analyze the functional groups in the nanoemulsion in the 400–4000 cm^{-1} frequency range. A dynamic light scattering (DLS) particle size analyzer (PSA, Zeta sizer Pro, Malvern Panalytical, UK) was used to measure droplet size under optimal conditions. A cleaned cuvette was filled with 12 μL of the sample to eliminate potential contaminants. The average particle size, ranging from 10–300 μm , was calculated to evaluate particle size distribution. The second cumulant of the polynomial fitting parameters was normalized to calculate the polydispersity index (PDI). Zeta potential (ELS with M3-PALS, Zetasizer Pro, Malvern Panalytical, UK) was measured using the constant current zeta mode within a size range of 100–3,800 μm .

2.2.3. Product Quality Assessment

The density of each sample was determined using pycnometer (Pycnometer 25 mL, Duran, Germany), followed by viscosity measurement using an Ostwald viscometer (Ostwald Capillary Viscometer, Cannon Instrument Company, USA). A 10 mL portion of the sample was placed into the larger bulb, then drawn into the smaller bulb until it surpassed the upper calibration mark. Once suction was released, the sample was allowed to flow downward, and the time required to pass from the upper to the lower mark of the smaller bulb was recorded. Repeated measurements ensured

Table 2. Physical characteristics of nanoemulsion.

Samples	Antioxidant	Emulsifier Type	pH	Density (g/mL)	Viscosity (cPs)	Specific gravity (g/mL)
HT	BSO	Tween 80	6.33±0.04	1.11±0.01	1.54±0.02	1.04±0.01
HW	BSO	WPI	6.51±0.02	1.23±0.02	1.53±0.03	1.09±0.02
HB	BSO	PEG	6.24±0.04	1.05±0.02	1.42±0.02	1.10±0.02
CT	Curcumin	Tween 80	6.43±0.01	1.17±0.02	1.40±0.01	1.09±0.01
CW	Curcumin	WPI	6.61±0.02	1.25±0.02	1.51±0.02	1.10±0.01
CB	Curcumin	PEG	6.15±0.02	1.12±0.02	1.30±0.02	1.05±0.02

consistent viscosity values. A total of 6 nanoemulsion formulations were tested, with three replicates conducted for each, and viscosity was calculated using Equation (1);

$$\eta_x = \frac{\eta_0 t_x \rho_x}{t_0 \rho_0} \quad (1)$$

where t_0 represents the flow time of the reference liquid (s), ρ_0 is the density of the reference liquid (g/mL), ρ_x refers to the density of the sample liquid (g/mL), t_x denotes the flow time of the sample liquid (s), η_0 = indicates the viscosity of the reference liquid (cP), and η_x corresponds to the viscosity of the sample liquid (cP).

Nanoemulsion stability was assessed using a centrifugation test. For 30 min, 40 mL of the sample were centrifuged at 1,000 rpm in tubes. Separation, creaming, aggregation, cracking, and precipitation were all monitored in the samples. A calibrated pH meter was used to measure the pH using a reference solution with a pH of 7. The pycnometer was used to measure specific gravity. Equation (2) was used to calculate specific gravity after the empty pycnometer was weighed, loaded with the nanoemulsion sample, and reweighed;

$$\text{Specific gravity} = \frac{W_s - W_0}{V_{\text{pycnometer}}} \quad (2)$$

where $V_{\text{pycnometer}}$ is pycnometer volume (mL), W_s is sample-filled pycnometer weight, and W_0 is empty pycnometer weight.

2.2.4. Antioxidants Activity

For antioxidant activity, 100 mg of sample was placed in a test tube and mixed with 1 mL of toluene. This was combined with 3.9 mL of 0.1 mM DPPH in toluene and vortexed for 30 s until homogeneous. The mixture was incubated at room temperature in the dark for 1 h. Absorbance was measured at 515 nm using a UV-Vis spectrophotometer. Toluene served as the blank control, and vitamin C as the positive control. DPPH scavenging activity was calculated using Equation (3).

$$\text{DPPH (\%)} = \frac{(\text{Abs control}) - (\text{Abs sample})}{\text{Abs control}} \times 100\% \quad (3)$$

2.2.5. Antibacterial Activity

The antibacterial assay sought to assess the efficacy of the nanoemulsions against Gram-positive *S. aureus* and Gram-negative *E. coli*. Samples (5–10%) were produced in a 10 mL volumetric flask. The bacterial suspensions were calibrated to an inoculum concentration of approximately 1×10^6 CFU/mL before testing. NA was dispensed into sterile Petri plates, and upon solidification, the prepared suspensions of *S. aureus* and *E. coli* were uniformly distributed across the surface using a sterile inoculating loop. Sterile disc papers were immersed in the samples and placed on the agar surface. The plates were incubated at 37 °C for 24 h, after which inhibition zones were measured in mm.

Table 3. PSA results of samples.

Samples	Antioxidant	Emulsifier Type	Particle size (nm)	Polydispersity Index (PI)
HT	BSO	Tween 80	264.4± 26.0	0.3993±0.050
HW	BSO	WPI	686.6±34.3	0.7227±0.060
HB	BSO	PEG	218.3±17.5	0.2713±0.030
CT	Curcumin	Tween 80	275.5±16.5	0.4133±0.040
CW	Curcumin	WPI	551.7±55.2	0.5233±0.070
CB	Curcumin	PEG	229.2±11.0	0.3491±0.040
BSO	-	-	1.402±0.120	0.8101±0.045
BSFO	-	-	395.2±39.5	0.7364±0.050
Curcumin	-	-	125.6±18.8	0.8841±0.030
PEG	-	-	0.5212±0.050	0.1936±0.020
WPI	-	-	12.58±1.26	0.3065±0.025
Tween 80	-	-	0.7227±0.110	0.4719±0.030

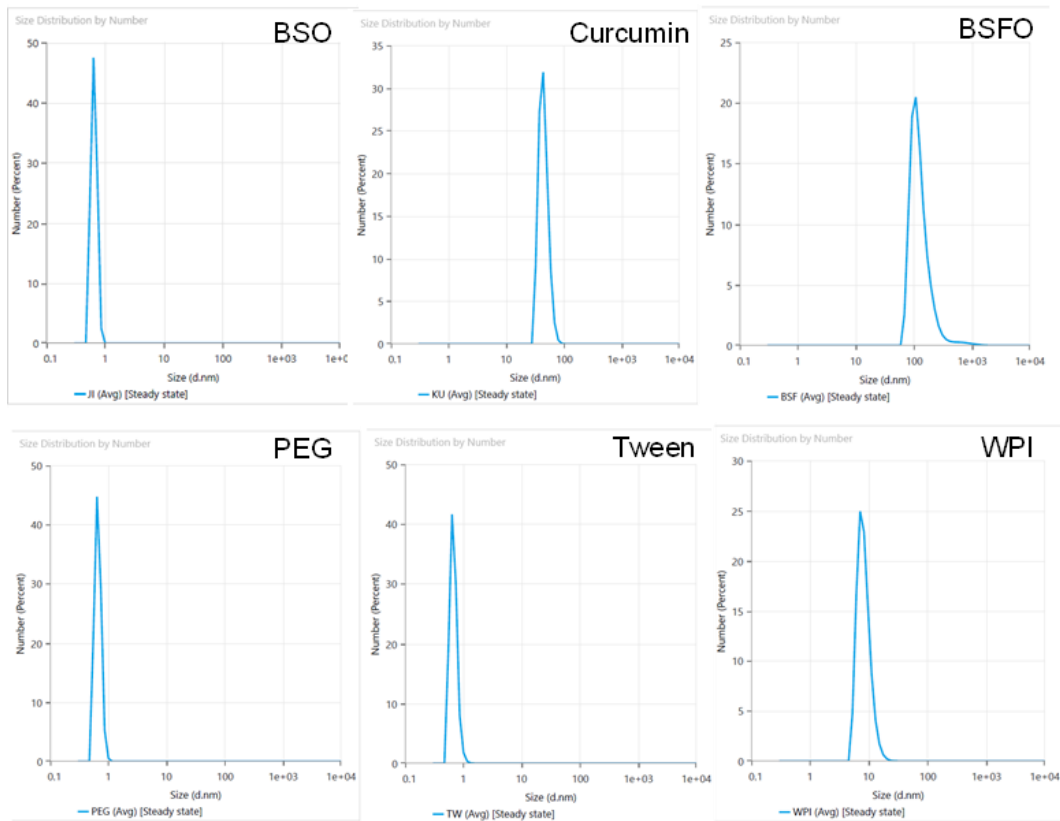


Figure 2. PSA results for the raw materials.

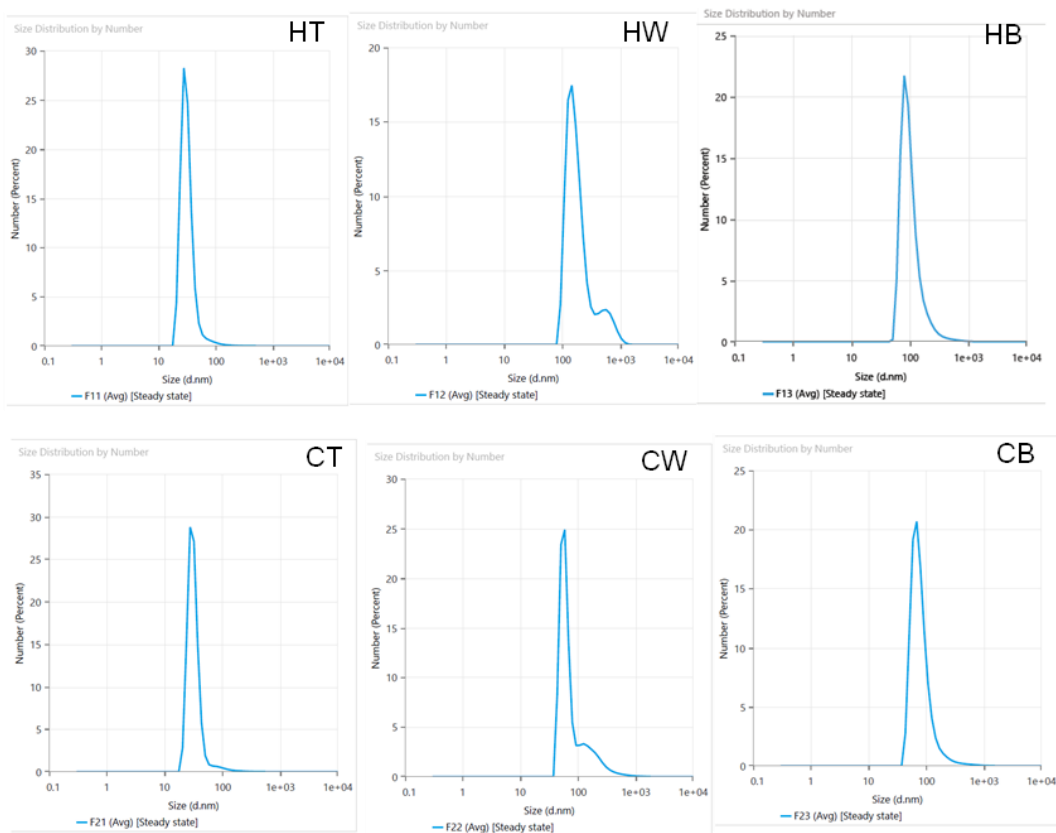


Figure 3. PSA results for the nano materials.

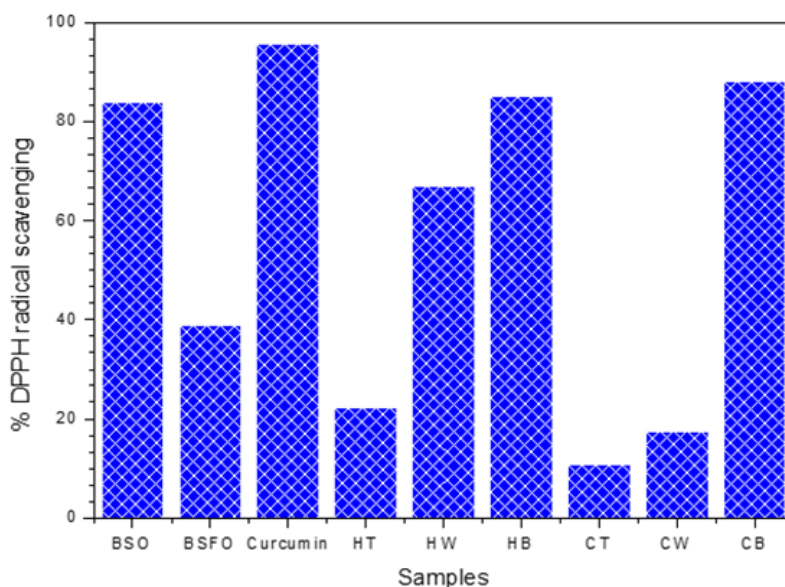


Figure 4. Antioxidants activity of sample by DPPH analysis.

2.2.6. Analysis Data

The data analysis utilized descriptive statistics to interpret the results of antibacterial activity, which was evaluated by measuring the inhibition zone against bacteria. Inferential analysis utilized one-way ANOVA and Tukey's post hoc test at a significance level of $\alpha = 0.05$ to differentiate among the formulations.

3. RESULTS AND DISCUSSIONS

BSFO is gaining recognition as a sustainable lipid source, attributed to its significant concentration of medium-chain fatty acids, especially lauric acid, which enhances antimicrobial activity and improves interfacial properties for emulsion formation. BSFO demonstrates potential as a carrier oil for nanoemulsion-based delivery systems. In addition, BSO is recognized as an effective herbal remedy, primarily due to thymoquinone (TQ), a compound known for its significant antioxidant, anti-inflammatory, and antimicrobial properties. Curcumin, a hydrophobic polyphenol derived from turmeric, is extensively researched for its potent antioxidant and anti-carcinogenic properties; however, its therapeutic efficacy is constrained by low solubility and bioavailability [19].

The FTIR spectroscopy depicted in Figure 1 examined the functional groups in nanoemulsions

with various emulsifiers. The absorption band appeared of Tween 80, curcumin, and PEG appeared in phenolic O–H (3100 cm^{-1}) and aromatic C=C stretching (2918 and 2846 cm^{-1}) [41]. The broad band at 3274 cm^{-1} observed in WPI, attributed to H-bonded OH stretching vibrations, is significantly larger than that of curcumin and PEG due to the contribution of N–H stretching vibrations associated with the hydrogen bonds of the protein. Moreover, WPI showed the peaks observed between 3200 and 2500 cm^{-1} as stretching vibrations of N–H and C–H bonds, then stretching vibration of the C=O at 1743 cm^{-1} [42]. Two prominent amide bands at 1620 and 1550 cm^{-1} were identified, corresponding to the C=O stretch (amide I) and the N–H bend and C–N stretch (amide II) for BSO and BSFO, respectively. For the nanoemulsions products, all the samples demonstrated absorption peaks in the ranges of 1700 – 1500 (C=O and amide I/II), 2900 – 2700 (C–H stretching), and 3500 – 3000 cm^{-1} (O–H/N–H stretching) [3]. The FTIR analysis revealed distinct peak shifts, particularly in the O–H and C=O regions, which suggest hydrogen bonding and molecular interactions among the components. Kabiriyel et al. [41] also stated that the interactions improved the stability of nanoemulsions and facilitated the formation of smaller, more uniform droplets, especially in PEG-based formulations.

To determine whether the nanoemulsion could

undergo phase separation because of gravity and whether centrifugal force could displace sample components from the centre of rotation, the centrifugation test was conducted during the first week. During phase separation, the lower-density phase rose to the top of the sample, while the higher-density phase sank to the bottom. Six samples were analysed, and the results showed no phase separation. The pH measurement was conducted to assess any significant changes in the acidity levels of the six samples, using consistent procedures depicted in Table 2. The average pH for the BSO-based nanoemulsion was 6.33 ± 0.04 , while the curcumin-based nanoemulsion had an average pH of 6.36 ± 0.01 . The findings showed no appreciable changes in pH, suggesting that the samples maintained stable acidity values. A pycnometer was used to test the specific gravity of samples. The six nanoemulsion samples had average specific gravities, densities, and viscosities ranging from 1.04–1.10 g/mL, 1.05–1.23 g/mL, and 1.30–1.54 cPs, respectively, according to the test results. The findings align with previous research by Tahir et al. [3], indicating that O/W nanoemulsions generally possess densities like water, accompanied by marginally increased viscosities that improve droplet stability and mitigate creaming or coalescence during storage.

The particle size of a nanoemulsion generally

falls between 1 and 100 nm. The PSA and DLS utilized in this study (Table 3) were specifically developed to assess the particle size of the final sample. The determination of particle size is achieved through the rapid detection of scattered light at a specific angle utilizing a photon detector [33]. Figures 2 and 3 depict the distribution of particle sizes (Z-average) in the nanoemulsion between approximately 229.2 ± 11.0 and 686.6 ± 34.3 nm. PEG can produce the smallest particle sizes among the investigated agents such as WPI and Tween 80. The HB and CB nanoemulsions made with PEG showed smaller particle size diameters than those made with other emulsifiers [43]. A PI value of less than 0.4 denotes particle homogeneity, while values exceeding this threshold indicate heterogeneity. To evaluate the stability and homogeneity of nanoemulsion formulations, the PI is a crucial measure for determining particle size distribution. Increased PI values indicate a reduction in particle homogeneity within the formulation [44]. Emulsifiers carry out by lowering surface tension, which aids in the creation of smaller droplets during homogenization, leading to nanoemulsions with significantly reduced particle sizes [43]. The PSA and PI values obtained in this study were lower than those reported by Saffarian et al. [44], who utilized Tween 80 (1% w/w) as an emulsifier and achieved an average particle size of

Table 4. Inhibition zone of antibacterial activity for samples.

Samples	Antioxidant	Emulsifier Type	Concentration (%)	Inhibition Zone (mm)	
				<i>E. coli</i>	<i>S. aureus</i>
HT	BSO	Tween 80	5	18.5±0.3	18.0±0.2
			10	23.0±0.5	19.5±0.4
HW	BSO	WPI	5	18.0±0.2	18.5±0.3
			10	20.5±0.4	22.0±0.5
HB	BSO	PEG	5	24.0±0.6	19.5±0.3
			10	27.0±0.7	24.5±0.6
CT	Curcumin	Tween 80	5	18.0±0.3	13.5±0.2
			10	23.5±0.5	15.5±0.4
CW	Curcumin	WPI	5	14.5±0.2	16.0±0.3
			10	15.5±0.3	23.0±0.5
CB	Curcumin	PEG	5	14.0±0.1	11.0±0.2
			10	16.0±0.4	16.0±0.3

483.4 nm for *Carum copticum* essential oil.

The antioxidant activity of BSFO-based nanoemulsions was assessed via the DPPH method to determine the percentage inhibition value shown in Figure 4. DPPH serves as an oxidizing agent in reactions with antioxidant compounds present in a sample (Table 4). The raw materials, BSO and curcumin, are well-established herbal remedies, globally distributed and extensively utilized in traditional medicine due to their potent antioxidant properties. Findings indicate that BSO and curcumin demonstrate inhibition rates of 84% and 96%, respectively. The formation of nanoemulsions may diminish antioxidant activity, likely attributable to the stability of nanoparticles, which, according to previous data, lack sufficient homogeneity—except for HB and CB, which demonstrate inhibition percentages of 85% and 88%, respectively [45].

Table 4 presents the antibacterial data for the nanoemulsion. Curcumin is a dimeric derivative of ferulic acid. The lipophilic nature of curcumin facilitates its integration into liposome bilayers. This enhances the permeability of the bilayer. In bacterial cells, curcumin may cause 1,2-dipalmitoyl-sn-glycero-3-phosphocholine (DPPC) membranes to break down. A bacterial agent with an inhibitory zone between 140 and 230 mm was demonstrated by the formation of curcumin-based nanoemulsion (CT, CW, and CB). The findings of the study indicate that the nanoemulsion exhibits a greater value than Sayyar et al. [46] demonstrated that curcumin nano dispersion, prepared at optimal proportions, possessed substantial antibacterial properties against *S. aureus* (35 mm) and *E. coli* (31 mm). The FTIR spectra of BSO-based nanoemulsions revealed the presence of significant functional groups linked to its bioactive compounds, notably TQ, which exhibits quinone C=O vibrations at 1743 cm^{-1} related to reactivity for the antimicrobial activity. BSO is rich in polyunsaturated fatty acids, particularly oleic acid, linoleic acid, omega-9, and omega-6, and is known for its notable stability against oxidative degradation. The antibacterial activity of BSO in food has been attributed to its diverse phytochemical constituents, such as thymoquinone, carvacrol, thymol, and thymoquinone, which have been shown to inhibit

pathogens including *Shigella*, *Staphylococcus aureus*, *Salmonella*, and *Listeria monocytogenes* [47]. The optimal activity of BSO-based nanoemulsion (HT, HW, and HB) is observed in HB, measuring 270 mm. The increased efficacy of BSO-based nanoemulsion compared to curcumin is attributed to the presence of TQ. TQ, the primary bioactive ingredient in black cumin seed oil, possesses anti-inflammatory, anti-apoptotic, and antioxidant properties [47].

4. CONCLUSIONS

The formulation of nanoemulsions based on BSFO was enhanced by incorporating the antioxidants curcumin or BSO. The formulations employed various emulsifiers, including PEG, Tween 80, and WPI. According to PSA data, nanoemulsions prepared with PEG as an emulsifier exhibited smaller and more uniformly dispersed particle sizes compared to those prepared with Tween 80 or WPI due to PEG size of 0.5212 ± 0.050 nm. The BSO-based nanoemulsion displayed smaller particle sizes than the curcumin-based nanoemulsion, as curcumin has a larger molecular size of 125.6 ± 18.8 nm. Among the samples, HB exhibited the smallest particle diameter at 218.3 ± 17.5 nm with their homogeneity of PI of 0.2713 ± 0.030 . The curcumin-based nanoemulsion (CB samples) demonstrated the highest antioxidant activity at 88.09%, which can be attributed to curcumin's superior antioxidant capacity (95.5%) compared to BSO's 83.9%. Meanwhile, the BSO-based nanoemulsion (HB samples) exhibited the strongest antibacterial activity, with inhibition zones of 24.5 ± 0.6 mm against *S. aureus* and 27.0 ± 0.7 mm against *E. coli*, attributable to TQ, the main component of black seed oil, which possesses anti-inflammatory, anti-apoptotic, and antioxidant properties. These findings demonstrate that BSFO nanoemulsions act as multifunctional bioactive carriers with significant potential in healthcare, pharmaceuticals, and functional foods. Future studies should focus on in vivo validation of bioavailability and safety, long-term stability testing under industrial conditions, and synergistic formulation strategies to enhance therapeutic and nutraceutical benefits, thereby facilitating translation into practical applications.

AUTHOR INFORMATION

Corresponding Author

Dewi Apri Astuti — Department Nutrition and Feed Technology, IPB University, Bogor-16680 (Indonesia);

orcid.org/0000-0001-8655-9304

Email: dewiaa@apps.ipb.ac.id

Authors

Novia Amalia Sholeha — College of Vocational Studies, IPB University, Bogor-16151 (Indonesia);

orcid.org/0000-0003-2912-2338

Tekad Urip Pambudi Sujarnoko — College of Vocational Studies, IPB University, Bogor-16151 (Indonesia);

orcid.org/0000-0001-8088-4851

Lilis Khotijah — Department Nutrition and Feed Technology, IPB University, Bogor-16680 (Indonesia);

orcid.org/0000-0001-5057-2777

Muhamad Baihaqi — Department of Animal Production and Technology, IPB University, Bogor-16680 (Indonesia);

orcid.org/0000-0002-9161-247X

Kokom Komalasari — Department Nutrition and Feed Technology, IPB University, Bogor-16680 (Indonesia);

orcid.org/0000-0002-0146-7855

Author Contributions

Conceptualization, N. A. S. and D. A. A.; Methodology, T. U. P.; Software, and Writing – Original Draft Preparation, N. A. S.; Validation, L. K., K. K., and M. B.; Writing – Review & Editing, D. A. A., T. U. P., L. K., and M. B.; Supervision, and Funding Acquisition, D. A. A. Project Administration, K. K.

Conflicts of Interest

The authors declare no conflict of interest.

ACKNOWLEDGEMENT

The authors acknowledge the Indonesian Ministry of Research under No. 027/E5/PG.02.00.PL/2024 with Contract No. IT3.D10/PT.01.03/P/B/2024 to Dewi Apri Astuti. The

authors express gratitude to the Directorate of Research and Innovation at IPB University.

DECLARATION OF GENERATIVE AI

Not applicable.

REFERENCES

- [1] N. Azmi, S. S. M. Lock, N. T. Berghuis, A. Sarwono, N. L. Zahra, A. Rahman, S. Waqas, and A. S. Farooqi. (2024). "Influence of Synthesis Approach and Formulation on the Physicochemical Properties of Chitin and Chitosan from Black Soldier Fly". *Results in Engineering*. **23** : 102401. [10.1016/j.rineng.2024.102401](https://doi.org/10.1016/j.rineng.2024.102401).
- [2] K. G. Felix-Sagaste, M. Garcia-Carrasco, L. A. Picos-Corrales, T. Gonzalez-Ruelas, and J. A. Rodriguez-Mercado. (2023). "Plant-Animal Extracts and Biocompatible Polymers Forming Oil-in-Water Emulsions: Formulations for Food and Pharmaceutical Industries". *Hybrid Advances*. **3** : 100072. [10.1016/j.hybadv.2023.100072](https://doi.org/10.1016/j.hybadv.2023.100072).
- [3] M. K. Ranasinghe, A. Ballon, S. de Lamo-Castellvi, M. Ferrando, and C. Guell. (2023). "Ultrafiltration of Black Soldier Fly (*Hermetia illucens*) and Mealworm (*Tenebrio molitor*) Protein Concentrates to Enhance Emulsifying and Foaming Properties". *Membranes*. **13** : 137. [10.3390/membranes13020137](https://doi.org/10.3390/membranes13020137).
- [4] I. Hsieh, T. Chou, and J. Chang. (2023). "Development and Evaluation of Functional Nanoemulsion Gel Using Eco-Friendly Fucoidan for Drug Delivery Applications". *Environmental Technology & Innovation*. **30** : 103130. [10.1016/j.eti.2023.103130](https://doi.org/10.1016/j.eti.2023.103130).
- [5] A. Falgayrac, V. Pellerin, C. Terrol, and S. C. M. Fernandes. (2024). "Turning Black Soldier Fly Rearing By-Products into Valuable Materials: Valorisation Through Chitin and Chitin Nanocrystals Production". *Carbohydrate Polymers*. **344** : 122545. [10.1016/j.carbpol.2024.122545](https://doi.org/10.1016/j.carbpol.2024.122545).
- [6] T. Chou, D. S. Nugroho, Y. Cheng, and J. Chang. (2020). "Development and Characterization of Nano-Emulsions Based

- on Oil Extracted from Black Soldier Fly Larvae". *Applied Biochemistry and Biotechnology*. **191** : 331-345. [10.1007/s12010-019-03210-y](https://doi.org/10.1007/s12010-019-03210-y).
- [7] U. Muslykhah, S. Phupaboon, C. Suriyapha, M. Matra, and M. Wanapat. (2024). "Encapsulation of Protein-Based Bioactive from Black Soldier Fly for Ruminant Feeding". *Journal of Agriculture and Food Research*. **18** : 101325. [10.1016/j.jafr.2024.101325](https://doi.org/10.1016/j.jafr.2024.101325).
- [8] S. A. Siddiqui, I. A. Harahap, J. Osei-Owusu, T. Saikia, Y. S. Wu, I. Fernando, R. Perestrelo, and J. S. Camara. (2024). "Bioconversion of Organic Waste by Insects: A Comprehensive Review". *Process Safety and Environmental Protection*. **187** : 1-25. [10.1016/j.psep.2024.04.122](https://doi.org/10.1016/j.psep.2024.04.122).
- [9] R. Dewanti, R. Martien, B. Ariyadi, and Z. Zuprizal. (2024). "Nano-Emulsified Black Soldier Fly Oil Concerning Performance Traits, Health, and Immunity of Broilers". *Poultry Science*. **103** : 104116. [10.1016/j.psj.2024.104116](https://doi.org/10.1016/j.psj.2024.104116).
- [10] R. Rahman, E. R. Laconi, D. A. Astuti, and A. Jayanegara. (2025). "In Vitro Evaluation of Various Treatments of Cocoa Pod Husk Bioconverted Using Black Soldier Fly as Ruminant Feed". *Journal of Animal Health and Production*. **13** : 600-608. [10.17582/journal.jahp/2025/13.3.600.608](https://doi.org/10.17582/journal.jahp/2025/13.3.600.608).
- [11] S. Warinhomhoun, S. Sanpinit, P. Chonsut, and N. Ngamdokmai. (2023). "Effects of Black Seed Oil Combined with Olive Oil or Honey on Antioxidant Activities, Phenolic Content, and Identification and Quantification of Thymoquinone, a Key Bioactive Compound". *Journal of Agriculture and Food Research*. **14** : 100891. [10.1016/j.jafr.2023.100891](https://doi.org/10.1016/j.jafr.2023.100891).
- [12] N. Naghsh, A. Hossein, Z. Kavyani, and V. Musazadeh. (2023). "The Effect of Nigella sativa (Black Seed) Supplementation on Body Weight and Body Composition: A GRADE-Assessed Systematic Review and Dose-Response Meta-Analysis of Randomized Controlled Trials". *Journal of Functional Foods*. **105** : 105565. [10.1016/j.jff.2023.105565](https://doi.org/10.1016/j.jff.2023.105565).
- [13] M. Jafari, K. Prastouei, and S. Abbaszaden. (2023). "Development of Curcumin-Loaded Nanoemulsion Stabilized with Texturized Whey Protein Concentrate: Characterization, Stability, and In Vitro Digestibility". *Food Science & Nutrition*. **12** : 1655-1672. [10.1002/fsn3.3860](https://doi.org/10.1002/fsn3.3860).
- [14] M. S. Lim, D. A. Astuti, and T. U. P. Sujarnoko. (2024). "The Effect of Curcuma xanthorrhiza Addition in the Post Transportation Ram Diet". *IOP Conference Series: Earth and Environmental Science*. **1359** : 012111. [10.1088/1755-1315/1359/1/012111](https://doi.org/10.1088/1755-1315/1359/1/012111).
- [15] C. Chiu, P. Huang, Y. Chan, P. Li, and W. Lu. (2024). "D-Limonene Nanoemulsion as Skin Permeation Enhancer for Curcumin Prepared by Ultrasonic Emulsification". *Journal of Agriculture and Food Research*. **15** : 100932. [10.1016/j.jafr.2023.100932](https://doi.org/10.1016/j.jafr.2023.100932).
- [16] N. Haq, F. Shakeel, M. M. Ghoneim, S. M. B. Asdaq, P. Alam, S. A. Alanazi, and S. Alshehri. (2023). "Greener Stability-Indicating HPLC Approach for the Determination of Curcumin in In-House Developed Nanoemulsion and Curcuma longa L. Extract". *Separations*. **10** : 98. [10.3390/separations10020098](https://doi.org/10.3390/separations10020098).
- [17] P. Gupta, S. Preet, Ananya, and N. Singh. (2022). "Preparation of Thymus vulgaris (L.) Essential Oil Nanoemulsion and Its Chitosan Encapsulation for Controlling Mosquito Vectors". *Scientific Reports*. **12** : 4335. [10.1038/s41598-022-07676-5](https://doi.org/10.1038/s41598-022-07676-5).
- [18] R. Enayatifard, J. Akbari, A. Babaei, S. S. Rostamkalaei, and S. Mohammad. (2021). "Anti-Microbial Potential of Nano-Emulsion Form of Essential Oil Obtained from Aerial Parts of Origanum vulgare L. as Food Additive". *Advanced Pharmaceutical Bulletin*. **11** : 327-334. [10.34172/apb.2021.028](https://doi.org/10.34172/apb.2021.028).
- [19] R. F. S. A. Ismail, M. A. E. Hassan, M. Moustafa, M. Al-Shehri, R. S. Alazragi, H. Khojah, A. A. El-Raghi, S. A. Abdelnour, and A. M. A. Gad. (2023). "The Influence of a Nanoemulsion of Cardamom Essential Oil on the Growth Performance, Feed Utilization, Carcass Characteristics, and Health Status of

- Growing Rabbits under a High Ambient Temperature". *Animals*. **13** : 2990. [10.3390/ani13182990](https://doi.org/10.3390/ani13182990).
- [20] W. Smulek and M. Jarzebski. (2023). "Hemp Seed Oil Nanoemulsion with Sapindus Saponins as a Potential Carrier for Iron Supplement and Vitamin D". *Reviews on Advanced Materials Science*. **62** : 20220317. [10.1515/rams-2022-0317](https://doi.org/10.1515/rams-2022-0317).
- [21] V. Kumar, R. Ul, R. Shams, and A. Hussain. (2022). "A Comprehensive Review on the Application of Essential Oils as Bioactive Compounds in Nano-Emulsion Based Edible Coatings of Fruits and Vegetables". *Applied Food Research*. **2** : 100042. [10.1016/j.afres.2022.100042](https://doi.org/10.1016/j.afres.2022.100042).
- [22] S. Kumar, N. Singh, L. S. Devi, S. Kumar, M. Kamle, P. Kumar, and A. Mukherjee. (2022). "Neem Oil and Its Nanoemulsion in Sustainable Food Preservation and Packaging: Current Status and Future Prospects". *Journal of Agriculture and Food Research*. **7** : 100254. [10.1016/j.jafr.2021.100254](https://doi.org/10.1016/j.jafr.2021.100254).
- [23] M. L. Medeleanu, A. C. Farcas, C. Coman, L. Leopold, Z. Diaconeasa, and S. A. Socaci. (2023). "Citrus Essential Oils-Based Nano-Emulsions: Functional Properties and Potential Applications". *Food Chemistry X*. **20** : 100960. [10.1016/j.fochx.2023.100960](https://doi.org/10.1016/j.fochx.2023.100960).
- [24] I. R. Singh and A. K. Pulikkal. (2022). "Preparation, Stability and Biological Activity of Essential Oil-Based Nanoemulsions: A Comprehensive Review". *OpenNano*. **8** : 100066. [10.1016/j.onano.2022.100066](https://doi.org/10.1016/j.onano.2022.100066).
- [25] S. M. El-Sayed and H. S. El-Sayed. (2020). "Antimicrobial Nanoemulsion Formulation Based on Thyme (*Thymus vulgaris*) Essential Oil for UF Labneh Preservation". *Journal of Materials Research and Technology*. **10** : 1029-1041. [10.1016/j.jmrt.2020.12.073](https://doi.org/10.1016/j.jmrt.2020.12.073).
- [26] R. Razavi, M. Amiri, H. A. Alshamsi, T. Eslaminejad, and M. Salavati-Niasari. (2021). "Green Synthesis of Ag Nanoparticles in Oil-in-Water Nano-Emulsion and Evaluation of Their Antibacterial and Cytotoxic Properties as Well as Molecular Docking". *Arabian Journal of Chemistry*. **14** : 103323. [10.1016/j.arabjc.2021.103323](https://doi.org/10.1016/j.arabjc.2021.103323).
- [27] F. M. M. Korn, A. N. Mohammed, and U. K. Moawad. (2023). "Using Some Natural Essential Oils and Their Nano-Emulsions for Ammonia Management, Anti-Stress and Prevention of Streptococcosis in Nile Tilapia (*Oreochromis niloticus*)". *Aquaculture International*. **31** : 2179-2198. [10.1007/s10499-023-01076-w](https://doi.org/10.1007/s10499-023-01076-w).
- [28] L. Durai, V. Gopakumar, and R. Nagarajan. (2020). "Preparation of Celery Essential Oil-Based Nanoemulsion by Ultrasonication and Evaluation of Its Potential Anticancer and Antibacterial Activity". *International Journal of Nanomedicine*. **15** : 7651-7666. [10.2147/IJN.S252640](https://doi.org/10.2147/IJN.S252640).
- [29] D. Liang, B. Feng, N. Li, L. Su, Z. Wang, F. Kong, and Y. Bi. (2022). "Preparation, Characterization, and Biological Activity of Cinnamomum cassia Essential Oil Nano-Emulsion". *Ultrasonics Sonochemistry*. **86** : 106009. [10.1016/j.ultsonch.2022.106009](https://doi.org/10.1016/j.ultsonch.2022.106009).
- [30] Y. Shi, M. Zhang, K. Chen, and M. Wang. (2022). "Nano-Emulsion Prepared by High Pressure Homogenization Method as a Good Carrier for Sichuan Pepper Essential Oil: Preparation, Stability, and Bioactivity". *LWT - Food Science and Technology*. **154** : 112779. [10.1016/j.lwt.2021.112779](https://doi.org/10.1016/j.lwt.2021.112779).
- [31] O. Sarheed, M. Dibi, and K. V. R. N. S. Ramesh. (2020). "Studies on the Effect of Oil and Surfactant on the Formation of Alginate-Based O/W Lidocaine Nanocarriers Using Nanoemulsion Template". *Pharmaceutics*. **12** : 1223. [10.3390/pharmaceutics12121223](https://doi.org/10.3390/pharmaceutics12121223).
- [32] M. Hosseinialhashemi, J. Tavakoli, and F. Ahmadi. (2021). "The Application of Pistacia khinjuk Extract Nanoemulsion in a Biopolymeric Coating to Improve the Shelf Life Extension of Sunflower Oil". *Food Science & Nutrition*. **9** : 920-928. [10.1002/fsn3.2057](https://doi.org/10.1002/fsn3.2057).
- [33] I. Tahir, J. Millevania, K. Wijaya, M. Mudasar, R. A. Wahab, and W. Kurniawati. (2023). "Optimization of Thiamine Chitosan Nanoemulsion Production Using Sonication Treatment". *Results in Engineering*. **17** : 100919. [10.1016/j.rineng.2023.100919](https://doi.org/10.1016/j.rineng.2023.100919).

- [34] V. K. Ananingsih, A. R. Pratiwi, B. Soedarini, and Y. A. S. Putra. (2024). "Formulation of Nanoemulsion Parijoto Fruit Extract (*Medinilla speciosa*) with Variation of Tween Stabilizers". *Frontiers in Nutrition*. **11** : 1398809. [10.3389/fnut.2024.1398809](https://doi.org/10.3389/fnut.2024.1398809).
- [35] Y. Li, B. Liu, J. Yang, J. Sun, J. Ran, X. Liang, and Y. Li. (2023). "Characterization of Polysaccharide from *Lonicera japonica* Thunb Leaves and Its Application in Nano-Emulsion". *Frontiers in Nutrition*. **10** : 1248611. [10.3389/fnut.2023.1248611](https://doi.org/10.3389/fnut.2023.1248611).
- [36] R. Adjonu, G. Doran, P. Torley, and S. Agboola. (2023). "Stability of Whey Protein Bioactive Peptide-Stabilised Nanoemulsions: Effect of pH, Ions, Heating and Freeze-Thawing". *International Journal of Food Science and Technology*. **58** : 1787-1794. [10.1111/ijfs.16292](https://doi.org/10.1111/ijfs.16292).
- [37] K. Haladyn, A. Wojdylo, and P. Nowicka. (2024). "Shaping the Bioactive Potential, Health-Promoting Properties, and Bioavailability of O/W Nanoemulsions by Modulating the Dose of a Carotenoid Preparation Isolated from *Calendula officinalis* L". *Food Chemistry*. **456** : 139990. [10.1016/j.foodchem.2024.139990](https://doi.org/10.1016/j.foodchem.2024.139990).
- [38] N. Hosseiniyeh, F. Mohtarami, H. Almasi, and S. Azizi. (2024). "Soy Protein Isolate Film Activated by Black Seed Oil Nanoemulsion as a Novel Packaging for Shelf-Life Extension of Bulk Bread". *Food Science & Nutrition*. **12** : 1706-1723. [10.1002/fsn3.3864](https://doi.org/10.1002/fsn3.3864).
- [39] M. Mehran, S. Masoum, and M. Memarzadeh. (2024). "Enhancing Stability and Antimicrobial Activity of Spearmint Essential Oil Nanoemulsion Through Formulation Optimization by Mixture Experimental Design and In Vitro Drug Release Study". *Journal of Dispersion Science and Technology*. **46** : 108-118. [10.1080/01932691.2023.2280093](https://doi.org/10.1080/01932691.2023.2280093).
- [40] G. Zuccari and S. Alfei. (2023). "Development of Phytochemical Delivery Systems by Nano-Suspension and Nano-Emulsion Techniques". *International Journal of Molecular Sciences*. **24** : 9824. [10.3390/ijms24129824](https://doi.org/10.3390/ijms24129824).
- [41] J. Kabiriyel, R. Jeyanthi, K. Jayakumar, A. Amalraj, P. Arjun, A. Shanmugarathinam, G. Vignesh, and C. R. Mohan. (2023). "Green Synthesis of Carboxymethyl Chitosan-Based Curcumin Nanoparticles and Its Biological Activity: Influence of Size and Conductivity". *Carbohydrate Polymer Technologies and Applications*. **5** : 100260. [10.1016/j.carpta.2022.100260](https://doi.org/10.1016/j.carpta.2022.100260).
- [42] C. Racz, L. Zsolt, C. Gabriel, G. Tomoaia, O. Horovitz, S. Riga, I. Kacso, G. Borodi, M. Sarkozi, A. Mocanu, C. Roman, and M. Tomoaia-Cotisel. (2023). "Curcumin and Whey Protein Concentrate Binding: Thermodynamic and Structural Approach". *Food Hydrocolloids*. **139** : 108547. [10.1016/j.foodhyd.2023.108547](https://doi.org/10.1016/j.foodhyd.2023.108547).
- [43] M. Yildirim, G. Sumnu, and S. Sahin. (2017). "The Effects of Emulsifier Type, Phase Ratio, and Homogenization Methods on Stability of the Double Emulsion". *Journal of Dispersion Science and Technology*. **38** : 807-814. [10.1080/01932691.2016.1201768](https://doi.org/10.1080/01932691.2016.1201768).
- [44] H. Saffarian, E. Rahimi, F. Khamesipour, and S. M. Dehkordi. (2024). "Antioxidant and Antimicrobial Effect of Sodium Alginate Nanoemulsion Coating Enriched with Oregano Essential Oil (*Origanum vulgare* L.) and Trachyspermum ammi Oil (*Carum copticum*) on Food Pathogenic Bacteria". *Food Science & Nutrition*. **12** : 2985-2997. [10.1002/fsn3.3979](https://doi.org/10.1002/fsn3.3979).
- [45] S. Rahmanzadeh-Ishkeh, H. Shirzad, Z. Tofighi, and M. Fattahi. (2025). "Preserving Phytochemical Properties and Antioxidant and Enzymes Activities in Raspberry Fruits with *Satureja sahendica* Essential Oil Nanoemulsion: A Strategy for Enhancing Raspberry Fruits Shelf Life". *Journal of Agriculture and Food Research*. **19** : 101655. [10.1016/j.jafr.2025.101655](https://doi.org/10.1016/j.jafr.2025.101655).
- [46] Z. Sayyar and H. Jafarizadeh-Malmiri. (2024). "Enhancing the Efficacy of Nano-Curcumin on Cancer Cells Through Mixture Design Optimization of Three Emulsifiers". *BMC Chemistry*. **18** : 62. [10.1186/s13065-024-01160-z](https://doi.org/10.1186/s13065-024-01160-z).
- [47] S. M. Kamal, W. M. Elsherif, and A. M. Faried. (2024). "Antibacterial Potential of

Black Seed Oil and Its Nanoemulsion
Against *Listeria monocytogenes* and
Salmonella Typhimurium in Yoghurt".

Journal of Advanced Veterinary Research.
14 : 1188-1194.